

Solving the crystallographic phase problem in i(AlPdMn)

K. S. Brown, A. A. Avanesov*, and V. Elser

Laboratory of Atomic and Solid State Physics, Clark Hall, Cornell University, Ithaca, NY 14853-2501
(February 1, 2008)

We apply a new technique for *ab initio* phase determination [Acta Crystallogr. Sect. A, **A55**, 48 (1999)] to solve for the average structure of the icosahedral (i) phase of AlPdMn. After an introduction to the crystallographic phase problem and a description of the method, we present a brief report of our findings for the structure of i(AlPdMn). Despite the use of data from extremely high quality samples, we find strong evidence of disorder in the structure, lending support to the random tiling model of quasicrystal stabilization.

61.44.Br, 61.10-i, 61.43.Bn

While X-ray diffraction is one of the most useful tools we have for solid-state structure determination for everything from simple metals to protein crystals, in a very real sense diffraction experiments only provide half of the information we need. X-ray diffractometers measure only the amplitudes of the various Fourier components of the electron density, not their relative phases. The recovery of the phases, given only the amplitudes, is termed the “phase problem”, or “phase retrieval”, in a more general context. Efforts to solve the phase problem can be broadly grouped into those that use additional data and those that do not. In the first category are three-beam interference measurements [1] and techniques such as isomorphous substitution and anomalous scattering at multiple wavelengths [2,3]. Methods of the second type are termed “direct” methods and were pioneered by Hauptman and Karle [4]. Algorithms which implement direct methods are highly evolved and very successful in solving structures of up to a few hundred atoms [5]. Recently, a technique called “Shake ‘n Bake” (SnB) [6,7] was developed expressly for application to more complex structures such as proteins. Common to all direct method algorithms currently in use is an iteration scheme which modifies phases to reproduce, either the statistical distribution of phase invariants (triplets, etc.) expected of an ideal gas of equal point scatterers, or known general features of the electron density (e.g. “solvent flattening”). Due to their iterative nature, the success rate of these algorithms, starting from random phases, is very unpredictable and in the case of complex structures frequently only a small fraction of a percent [6]. One possible reason for this behavior is that like all iterative optimization schemes [8] these methods can become stuck in fixed points that are locally but not globally optimal. This phenomenon is known as “stagnation” in the image processing literature [10].

Unfortunately, current direct methods are completely unsuitable for solving i(AlPdMn) and all other quasicrystalline structures for two reasons. On the one hand, the properties of the quasicrystalline state require that

their Bragg peaks be indexed by more than three indices; icosahedral phases, in particular, have an average structure that requires six dimensions (6D) to represent periodically [11]. Furthermore, an atomistic three dimensional electron density is obtained by cutting a density in the higher dimensional space. The latter need not be concentrated at points; rather, one expects the analogues of atoms — “atomic surfaces” — to be rather extended in the additional dimensions. The inability of established direct methods to deal with these features of quasicrystalline charge distributions recently led one of us [12] to introduce a new method for phase retrieval, called the principle of minimum charge (minQ). This new method differs from previous direct methods in three important respects: it is not iterative or stochastic, it does not rely on atomicity of the charge density, and it is applicable in arbitrary dimension. A direct method that works in arbitrary dimension is useful not only for quasicrystals but also in image reconstruction.

While an extended discussion of the foundations of minQ is available elsewhere [12], the central idea can be stated very simply: *the correct phases are such that the total charge Q is a minimum*. This claim has its roots in the following observation. The minimum average charge density (equivalently, Q) required to restore positivity to a tentative density reconstruction is determined by the deepest minimum in the electron density; the large number of free parameters (phases) implies that the minimum Q is achieved when a correspondingly large number of minima in the electron density are exactly degenerate and represents the relatively large fraction of the unit cell volume — in a correct reconstruction — having negligible charge density.

Past methods to solve the phase problem in quasicrystals have been indirect and have relied on observations about the diffracted intensities [13] or relationships of the actual structure to closely related approximant structures [14]. There has also been some use of the maximum-entropy method [15] in quasicrystal structure determination [16], but this work has focused on structure re-

finement and not *ab initio* phase recovery. Our selection of i(AlPdMn) as a proving ground for the minQ method had a threefold motivation: as previously stated, existing direct methods are not applicable, important structural details were heretofore unknown, and a wealth of diffraction data for extremely high quality samples is available [17].

The Fourier series for the electron density, for crystals as well as quasicrystals, may be written as

$$\rho(\mathbf{r}) = F_0 + 2 \sum_{\mathbf{q} \in \Lambda^+} F_{\mathbf{q}} \cos(\mathbf{q} \cdot \mathbf{r} - \phi_{\mathbf{q}}) \quad (1)$$

where Λ^+ is a set of nonzero reciprocal lattice vectors corresponding to the x-ray data (each element representing a $\{\mathbf{q}, -\mathbf{q}\}$ pair). F_0 is the average charge density whose minimization is the goal of any algorithm based on minQ. We assume the size of Λ^+ is large enough so as to make truncation errors negligible. If we specialize to the case of structures with centrosymmetry, as in i(AlPdMn), $\rho(\mathbf{r}) = \rho(-\mathbf{r})$ and $\phi_{\mathbf{q}}$ can be either 0 or π . We may therefore replace the phases in the argument of the cosine with overall multiplicative signs $s_{\mathbf{q}} = \pm 1$. Our separation of F_0 from the rest of the diffraction amplitudes in Eqn. (1) emphasizes its practical difference from other amplitudes in that F_0 is not measured. Given a maximum spatial frequency in Λ^+ , we can evaluate the density on a finite grid $\mathcal{G}$. Consequently, we only deal with a matrix of numbers $\mathbf{F}$ with entries

$$\mathbf{F}_{\mathbf{r}\mathbf{q}} = 2F_{\mathbf{q}} \cos(\mathbf{q} \cdot \mathbf{r}) \quad \mathbf{r} \in \mathcal{G} \quad \mathbf{q} \in \Lambda^+. \quad (2)$$

Imposing positivity at our set of grid points, the minimum charge principle immediately leads to a linear optimization problem:

$$\text{minimize : } F_0 \quad (3)$$

$$\text{subject to : } F_0 + \mathbf{F} \cdot \mathbf{s} \geq 0 \quad (4)$$

$$s_{\mathbf{q}} \in \{-1, 1\} \quad (5)$$

This type of problem is referred to in the optimization literature as a mixed-integer program (MIP) [18,19]: the objective function and constraints are linear in the unknowns, while some of the unknowns are required to take discrete (integer) values. This general type of problem has a long history in operations research, with applications to scheduling, job assignment, and set partitioning to name a few examples [20]. The traveling salesman problem is an example of an integer program for which very large instances have recently been solved. The minimum charge formulation of the centrosymmetric phase problem most closely resembles a particular class of MIP known as the multidimensional 0-1 knapsack problem, a $\mathcal{NP}$ -hard combinatorial optimization problem [12,21].

Even for a modest-sized problem like i(AlPdMn), the search tree for 500 measured reflections (unknown signs) has 2^{500} leaves, so search by enumeration is impossible.

Several algorithms have been developed in an attempt to solve problems of the kind specified by Eqns. (3)–(5). One such algorithm, known as “branch and bound” (BnB), has been used to solve some of the largest traveling salesman problems to date [22]. The basic idea of BnB is to use information about bounds on the objective function to reduce the search space.

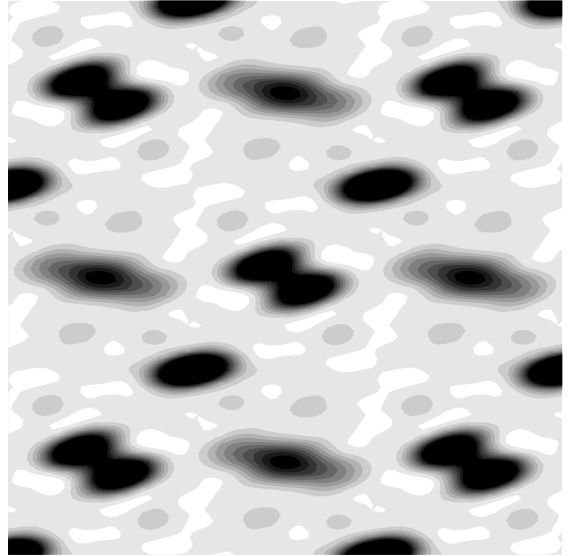


FIG. 1. Reconstructed electron density in the 5-fold plane of the 6D unit cell. Darker regions correspond to higher charge density and can be identified with the three types of atomic surface proposed by the authors of Ref. 17.

The feature of integer and mixed integer programming problems that makes them so difficult is that the optimization is over a nonconvex set. If we were to relax the integer constraints on the signs and allow $s_{\mathbf{q}} \in [-1, 1]$, we have a related problem called a linear program (LP). Linear programs are *not* $\mathcal{NP}$ -hard so there exist a variety of polynomial time algorithms to solve them [23]. Though the LP for the phase problem is unphysical, LP solutions of integer and mixed integer programs (known as “relaxations”) serve as upper (lower) bounds on the unrelaxed integer programs whose goal is maximization (minimization). We may use this information to reduce the search space in the following way. Suppose we are at depth d in the tree, meaning we have fixed the first $d - 1$ signs at ± 1 values. Suppose also we have some information about the upper bound on the charge, whether it be via feasible though non-optimal solutions, or through *a priori* knowledge. We then solve two relaxed LP problems; one in which $s_d = 1$ and one for which $s_d = -1$, the relaxation occurring on all signs with index greater than d . If one of the relaxed problems yields a value for the charge that is greater than our current best value, we know the solution *cannot* lie in that portion of the tree and we may prune that entire branch.

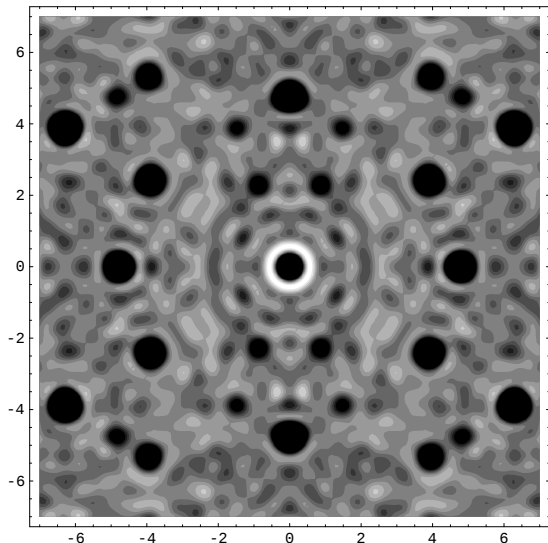


FIG. 2. Contour plot of the i(AlPdMn) electron density within an icosahedral mirror plane centered on the Mackay cluster (a center of icosahedral symmetry). The darker regions correspond to regions of higher electron density. Pairs of atoms at unphysically short separation are manifestations of partial site occupation in the average structure. The units on both axes are Å.

The BnB search strategy that has proven most effective is a variation of the “breadth-first” search, with the branching order specified by the Fourier amplitudes. Thus signs corresponding to large amplitudes are branched on first, while the very low amplitude signs remain relaxed throughout the optimization. A basic parameter of the search is an imposed upper bound on the charge. Beginning at the root, the tree is searched exhaustively by branching on successively smaller amplitude signs until the LP relaxations exceed the imposed upper bound. This limits the depth of search into the tree, with deeper searches corresponding to higher imposed bounds. Our experience with i(AlPdMn) reproduces the behavior seen in studies with simulated diffraction data, where a particular branch of the search tree is explored much deeper than all other branches (given our imposed bound on the charge). Were one to increase the imposed bound, eventually this distinguished branch would be the first to reach the top of the tree and yield the solution of the optimization problem. This is hardly necessary, however, since the important characteristics of the solution (large amplitude signs) have already been determined when the distinguished branch first appears.

The efficiency of the algorithm is improved by reducing the number of constraints in Eqn. (4). Since each inequality is associated with a point of the grid $\mathcal{G}$, we wish to choose the smallest $\mathcal{G}$ consistent with the Fourier sampling theorem which applies to our particular space group. If G is the corresponding point group, Eqn. (2) generalizes to

$$\mathbf{F}_{\mathbf{r}\mathbf{q}} = \frac{F_{\mathbf{q}}}{O(G_{\mathbf{q}})} \sum_{g \in G} \cos(\mathbf{q}_g \cdot \mathbf{r} + \Phi(\mathbf{q}_g)), \quad (6)$$

where Φ is the phase function of the space group [25] and $O(G_{\mathbf{q}})$ is the order of the subgroup of G that fixes any particular element of the orbit, $\mathbf{q}_g$. The columns of $\mathbf{F}_{\mathbf{r}\mathbf{q}}$ thus correspond to symmetry orbits of reflections. We make $\mathbf{F}$ square and invertible by choosing the number of grid points to equal the number of reflection orbits in the data set (plus one additional point for $\mathbf{q} = 0$). The locations of the grid points within the fundamental region of the space group are determined by making $\mathbf{F}$ well-conditioned. We use a simple procedure which starts with random locations and performs conjugate gradient displacements that maximize $\log \det \mathbf{F}^t \mathbf{F}$ [24].

We now present our results for the structure of i(AlPdMn), with space group $F\bar{5}3\frac{2}{m}$. Due to space constraints we give a detailed report elsewhere [26]. The minimum charge phase determination was performed with 499 of the 503 symmetry inequivalent reflections in the data set of Boudard et al. [17]. The deepest BnB search went to depth 84 and required 2730 LP evaluations. A distinguished branch already appeared in shallow searches with depth as small as 10. As a 6D structure i(AlPdMn) is relatively simple and the phase determination effort is not so much that of *finding* the solution but more the process of refining (extending) the solution to the weaker reflections.

To minimize on interpretation we only give the reconstructed electron density, that is, we do not attempt to identify atomic surfaces with idealized polyhedra and specific chemical occupation domains. Also, we note that since our electron density is derived from Bragg reflection data, it represents the *average* structure and may therefore possess unphysically short interatomic distances, or other manifestations of disorder. Strong indications of partial/mixed occupational disorder were already found prior to phase determination in the process of normalizing the experimental data [27].

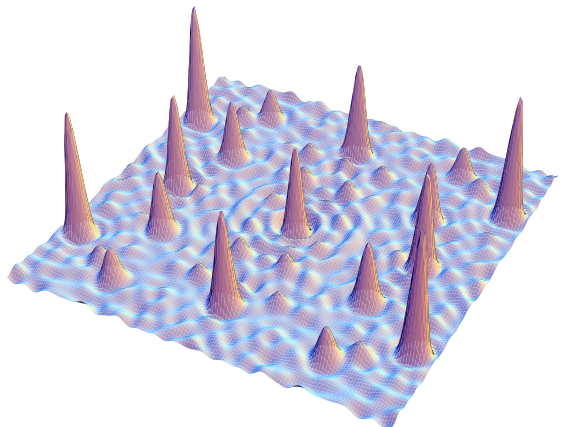


FIG. 3. Height representation of the electron density in Fig. 2.

The main features in the electron density are seen in a “5-fold plane”, Figure 1 — a two dimensional section that is commensurate with the 6D lattice and invariant with respect to a 5-fold rotation. The compact concentrations of charge in this plane are consistent with the three atomic surface model derived by Boudard et al. [17] using Patterson analysis. There is also some evidence in our reconstructed “surfaces” of features that go beyond the naive tiling models of quasicrystalline structure. For example, deviations from a straight “cigar” shape indicate context dependent shifts from ideal tile vertices.

By far the most conspicuous feature of the reconstructed atomic surfaces is their rounded character. We believe this correctly reflects the strong damping of intensities with the perpendicular component of the 6D wave vector and is not an artifact of Fourier truncation. A definitive test will require a larger x-ray data set. The rounding of the atomic surfaces, particularly in the three dimensions perpendicular to physical space, is expected in the random tiling scenario [28], where the average structure is effectively a superposition of many tile rearrangements. Boundaries of the averaged atomic surfaces (in the perpendicular dimensions) would not be sharp leading to numerous partially occupied sites and apparent unphysically short interatomic separations. Our reconstructed electron density in a mirror plane through the origin in physical space, Figs. 2 and 3, illustrates these effects. Well defined atomic positions occur in the second shell and correspond to the Mackay cluster. The sites of the first shell, at vertices of a small dodecahedron, are only partially occupied to avoid short interatomic separations.

We have described a new algorithm for direct method phase determination based on optimization ideas from operations research. Our application of the method to i(AlPdMn) shows the importance of statistical disorder in the structure. We are currently studying the complexity of phase retrieval in general, including the effects of diffraction data resolution. In addition, we are applying the method to other instances of phase retrieval, including two-dimensional images and structure determination of small biological molecules.

ACKNOWLEDGMENTS

We thank M. P. Teter for help in data normalization. K. S. Brown is supported by an NSF graduate research fellowship. A. A. Avanesov was supported under NSF grant DMR-9820543 and DMR-MRSEC-9632275.

* Present address: Department of Physics, University of Oregon, Eugene, OR 97403

- [1] Q. Shen and R. Colella, *Nature* **329**, 232 (1987).
- [2] J. Drenth, *Introduction to Protein X-Ray Crystallography* (Springer, New York, 1999).
- [3] Y. Okaya and R. Pepinsky, *Phys. Rev.* **103**, 1645 (1956).
- [4] H. Hauptmann and J. Karle, *The Solution of the Phase Problem. I. The Centrosymmetric Crystal* (American Crystallographic Association Monograph No. 3, Polycrystal Book Service, New York, 1953).
- [5] G. M. Sheldrick, *Acta Crystallogr.* **A 46**, 467 (1990).
- [6] <http://www.hwi.buffalo.edu/SnB/>
- [7] C. M. Weeks, G. T. DeTitta, R. Miller, H. A. Hauptman, *Acta Crystallogr.* **D 49**, 179 (1993).
- [8] SHELX [5] uses a stochastic annealing procedure [9] while SnB uses effectively zero temperature annealing, though the merits of one versus the other are unclear.
- [9] S. Kirkpatrick, C. D. Gelatt Jr., and M. P. Vecchi, *Science* **220**, 671 (1983).
- [10] J. R. Fienup and C. C. Wackerman, *J. Opt. Soc. Am. A* **3**, 1897 (1996).
- [11] V. Elser, *Phys. Rev. B* **32**, 4892 (1985); J. W. Cahn, D. Schechtman, and D. Gratias, *J. Mat. Res.* **1**, 13 (1986); V. Elser, *Acta Crystallogr.* **A 42**, 36 (1986).
- [12] V. Elser, *Acta Crystallogr.* **A 55**, 489 (1999).
- [13] M. Cornier-Quiquandon *et. al.*, *Phys. Rev. B* **44**, 2071 (1991); M. deBoissieu *et. al.*, *J. Phys.: Condens. Matter* **6**, 10725 (1994).
- [14] S.-Y. Qiu and M. V. Jaric, in *Quasicrystals*, edited by M. V. Jaric and S. Lundqvist (Singapore, World Scientific, 1990).
- [15] G. Bricogne, *Acta Crystallogr.* **A 40**, 410 (1984); *Acta Crystallogr.* **A 44**, 517 (1988).
- [16] M. deBoissieu, R. J. Papoular, C. Janot, *Europhys. Lett.* **16**, 343 (1991); W. Steurer, T. Haibach, and B. Zhang, *Acta Crystallogr.* **B 49**, 661 (1993).
- [17] M. Boudard *et. al.*, *J. Phys.: Condens. Matter* **4**, 10149 (1992).
- [18] L. Wolsey, *Integer Programming* (John Wiley, New York, 1998).
- [19] The presence of the single continuous variable F_0 makes minQ optimization a mixed, as opposed to pure, integer program.
- [20] G. Nemhauser and L. Wolsey, *Integer and Combinatorial Optimization* (John Wiley, New York, 1988).
- [21] E. Y.-H. Lin, *INFOR* **36**, 274 (1998).
- [22] D. Applegate, R. Bixby, V. Chvátal and W. Cook, *Doc. Math. J. DMV*, 645 (1998).
- [23] G. B. Dantzig, *Linear Programming and Extensions* (Princeton University Press, Princeton, 1963).
- [24] V. Elser and K. S. Brown, in preparation.
- [25] N. D. Mermin, *Rev. Mod. Phys.* **64**, 3 (1992).
- [26] V. Elser and K. S. Brown, in preparation.
- [27] C. L. Henley, V. Elser and M. Mihalkovic, *Z. Kristallogr.* **215**, (2000), in press.
- [28] V. Elser, *Phys. Rev. Lett.* **54**, 1730 (1985).